

UDC 541.123:546.175:546.65

Formation of polyfunctional photocatalytically active layered oxide materials using coordination nitrates REE and alkali metal as precursors

Dryuchko Oleksandr^{1*}, Bunyakina Natalia², Shefer Oleksandr³,
Laktionov Oleksandr⁴, Halai VasyI⁵, Pleshkan Daniil⁶

¹ National University «Yuri Kondratyuk Poltava Polytechnic» <https://orcid.org/0000-0002-2157-0526>

² National University «Yuri Kondratyuk Poltava Polytechnic» <https://orcid.org/0000-0003-4241-5127>

³ National University «Yuri Kondratyuk Poltava Polytechnic» <https://orcid.org/0000-0002-3415-349X>

⁴ National University «Yuri Kondratyuk Poltava Polytechnic» <https://orcid.org/0000-0002-5230-524X>

⁵ National University «Yuri Kondratyuk Poltava Polytechnic» <https://orcid.org/0000-0002-1205-7923>

⁶ National University «Yuri Kondratyuk Poltava Polytechnic» <https://orcid.org/0000-0003-3264-7776>

*Corresponding author E-mail: dog.chemistry@gmail.com

The information on alkaline coordination nitrates of rare earth elements of the cerium subgroup - precursors of promising modern multifunctional materials - on the conditions of their formation and existence, the nature of chemical bonding, composition, structure, shape of Ln coordination polyhedra, type of ligand coordination, existence of isotype series is generalized. on stoichiometry of structure, structure, the found out characteristic properties. The obtained data are the basis for detection, identification, control of the phase state of processing objects in the preparatory stages in the formation of nanostructured oxide composite systems of lanthanides and transition elements of special purpose, with catalytic and photocatalytic activity, self-cleaning coating with hydrophilic properties; development of various combined methods of their activation

Keywords: alkaline coordination nitrates of lanthanides, formation conditions, crystal structure of compounds, transformations with physical activation.

Формування поліфункціональних фотокаталітично активних шаруватих оксидних матеріалів з використанням координаційних нітратів РЗЕ та лужних металів як прекурсорів

Дрючко О.Г.^{1*}, Бунякіна Н.В.², Шефер О.В.³,
Лактіонов О.І.⁴, Галай В.М.⁵, Плешкань Д.П.⁶

^{1, 2, 3, 4, 5, 6} Національний університет «Полтавська політехніка імені Юрія Кондратюка»

*Адреса для листування E-mail: dog.chemistry@gmail.com

Комплексним системним дослідженням взаємодії структурних компонентів у системах нітратів рідкісноземельних і ІА групи елементів періодичної системи – прекурсорів сучасних багатокомпонентних оксидних поліфункціональних матеріалів на їх основі – встановлено утворення чисельного класу лужних координаційних нітратів лантаноїдів. Виявлені об'єктивні закономірності мають фундаментальну і прикладну цінність, поглиблюють розуміння про: хімічні і фізичні властивості Ln, їх комплексоутворюючу здатність; можливість утворення і існування в аналогічних системах асоційованих нових фаз, їх атомно-кристалічну будову, стійкість і стабільність; вплив природи лантаноїдів і лужних металів на структуру комплексних аніонів і сполук у цілому; індивідуальність Ln комплексів; існування ізотипних за складом і структурою груп сполук за природними рядами лантаноїдів і лужних металів; роль NO₃⁻ груп в стереохімії цього класу нітратів; роль води у формуванні найближчого оточення іонів Ln³⁺ – комплексоутворювачів. Одержана система знань про перетворення у системах РЗЕ-вмісних нітратних попередників і кристалохімічні властивості зразків координаційних нітратів Ln набуває особливу цінність при формуванні наноструктурованих шаруватих перовскитоподібних сполук лантаноїдів і перехідних елементів (в тому числі титану та інших), твердих розчинів на їх основі; при встановленні технологічно-функціональних залежностей між способом приготування, варіативністю методу активації технологічних систем, методологією виготовлення цільового продукту і його фазовим складом, параметрами решіток, величиною питомої поверхні, морфологією складових частинок, активністю шарів самоочищуючихся композицій з фотокаталітичними і гідрофільними властивостями, сформованими на поверхні конструкційних і спеціального призначення елементах; при практичній реалізації інноваційних проєктів розкладання води для цілєї отримання водню, розкладання токсичних органічних речовин у розчинах і повітрі, неповного окиснення вуглеводів; при отриманні нових перовскитоподібних фаз та в інших сферах

Ключові слова: лужні координаційні нітрати лантаноїдів, умови утворення, кристалічна будова сполук, перетворення з фізичною активацією.



Introduction

Currently, the search for methods and complex technologies to create new and improve existing regulations for the production of perfect multifunctional oxide materials of transition and rare earth elements with the structure of defective perovskite, garnet with reproducible properties by low-temperature methods of "soft chemistry" and precursors. They have a complex structure and in scientific and technological terms are difficult objects that are intensively studied [1–11]. Therefore, modern materials science, which is based on them, requires regulatory solutions simple in configuration, low-speed, energy efficient, characterized by scale, and with the ability to reproduce products with a given homogeneity, stability, and a set of predefined characteristics.

Review of the research sources and publications

There are many methods for the synthesis of these oxide multicomponent materials [2–13], based on different physical and chemical principles. The main ones are:


- high-temperature method of solid-phase chemical reactions;
- condensation liquid-phase methods for obtaining nanosized oxide materials based on:
 - various variants of mixing of initial components (chemical precipitation (coprecipitation); sol – gel; hydrothermal; complexonate homogenization; solvent replacement; synthesis under the action of microwave radiation);
 - rapid thermal decomposition of precursors in solution (spray drying; rapid expansion of supercritical fluid solutions; cryochemical);
 - self-igniting (glycine-nitrate; Pechini method; cellulose (fabric, paper) technology; pyrolysis of polymer-salt films).

The choice of using a particular method depends on the chemical nature of the obtained compounds, the size and morphological characteristics of the particles of the synthesis products, the conditions, and method of formation of the latter; the material and condition of the surface, the shape of the samples on which the coating is applied; capabilities of available technical equipment, etc. These methods are used both independently of each other and in combination.

Recently, titanium dioxide has attracted special attention due to new unique prospects for its use in the form of nanostructured materials and nanocomposites with controlled morphological, physicochemical and optical properties. TiO₂, which has high chemical and thermal stability, as well as impurity levels in the electronic structure of the material, created by a given type of doping, is unique for building on its basis new effective functional materials used in photocatalysis and photovoltaics, sensory, catalysis, for liquid chromatography and other areas.

The essence of the FC properties of TiO₂ is that in the volume of a semiconductor particle under the influence of electromagnetic radiation, electron - hole pairs are generated, which, upon reaching the surface of a TiO₂

particle, enter redox reactions with adsorbed molecules. For titanium dioxide, the process is as follows



In this case, part of the electrons and holes can undergo recombination in the bulk or on the surface of TiO₂. For the effective occurrence of photocatalytic processes, it is necessary that redox reactions involving an electron-hole pair be more effective than recombination processes.

The advantages of the photocatalytic method of purification are well known: 1) the ability to oxidize almost any organic matter and also a number of inorganic, such as CO, H₂S, HCN, NH₃, NO_x, etc.; 2) the method works at room temperature and atmospheric pressure; 3) it is possible to oxidize even small concentrations of pollutants, cleaning of which by other methods is economically unprofitable; 4) for the implementation of the method of photocatalytic purification does not require additional reagents, because the oxidant is oxygen.

However, for the photocatalytic method of air purification, a number of disadvantages are known, such as:

- 1) a relatively low purification rate;
- 2) the need to use ultraviolet light sources in the case where the photocatalyst is titanium dioxide;
- 3) low adsorption capacity of most simple photocatalysts;
- 4) the possibility of formation of intermediate products during the oxidation of high concentrations of pollutants.

Therefore, the development of new photocatalytic systems that would overcome these shortcomings is the subject of an urgent series of modern studies.

Definition of unsolved aspects of the problem

When creating and heat treatment of materials based on titanium dioxide, it is necessary to take into account the possibility of surface and bulk defects of the TiO₂ crystal lattice (due to the existence of phase diversity in the range of O / Ti < 2 ratios on the phase diagram of the Ti - O system [14]) and detection their significant effect on the photochemical properties and photoinduced hydrophilic ability of the synthesis products [15].

Available information on the state and possible directions of improvement of technologies for creating such materials, current requirements for their stability and reproducibility of properties, expansion of their use [1–15], manifestation of high activity of low-crystallized particles of structural components formed by solvent thermolysis [16], new information on reactivity and transformation of layered perovskite-like oxides, stabilization of photocatalytic and sensory-active crystalline modification of anatase due to NO₃⁻ ions [17], doping of Ln₂O₃ [18, 19] in obtaining TiO₂ from solutions [20] initiated the continuation of our study. Today, ways to control the technical parameters of the target products are through the choice of composition, synthesis conditions, and method of processing.

One of the most promising classes of complex oxide materials of rare earth elements and titanium are

nanostructured layered perovskite-like compounds and solid solutions based on them. Depending on the composition and structure, they have a wide range of physicochemical properties. Presented in this paper perovskite-like layered titanates belong to the homologous series $(Me, Ln)_{n+1} Ti_n O_{3n+1}$, where $Ln - La - Nd$, $Me - Li - Cs$, n is the number of nanolayers of perovskite (Ruddlesden-Popper phases; with a thickness of approximately one layer 0.5 nm). Accordingly, $MeLnTiO_4$ in its structure contains one nanolayer of perovskite, $Me_2Ln_2Ti_3O_{10}$ - three. Perovskite-like nanolayered titanates were obtained and studied by the authors of [21- 24]. Figure 1 shows an extended unit cell for $Me_2Ln_2Ti_3O_{10}$ ($Ln - La, Nd$; $Me - Li, K$) [23] and $Na_2Ln_2Ti_3O_{10}$ [24].

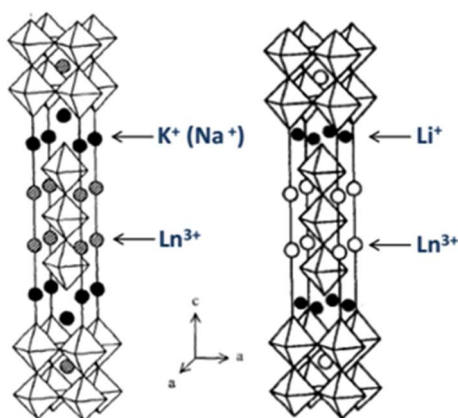


Figure 1 – Extended elementary cells of Ruddlesden-Popper phases, [23, 24]

So oxides of $K_2Nd_2Ti_3O_{10}$ (as an example) crystallize in a tetragonal structure. The spatial group for these compounds is defined as $I4 / mmm$. The thickness of layered oxides of this type is characterized by three titanium-oxygen octahedra [$Nd_2Ti_3O_{10}$], alternating with each other and separated by alkali metal cations, in this case, potassium cations, between the layers. The lattice parameter c ($\approx 30\text{\AA}$) indicates the displacement of adjacent perovskite layers by $1/2$. The neodymium cation is located in the center of the perovskite lattice and is characterized by a 12-coordinated oxygen environment. The alkali metal cation is located in the interlayer space and is usually 9-coordinated [25].

The layered structure, consisting of lamellar particles, is stored by the product when kept in humid air and confirmed by scanning electron microscopy [26]. The identified stability of the systems recommends them as promising photocatalysts in conditions close to their use and is important for other innovative areas of their applications.

Analysis of recent publications shows that titanium dioxide is mainly used in thin film form, which most effectively implements its properties necessary for photocatalysis, solar energy, sensors, self-cleaning coatings, and more.

And the practical implementation of modern technologies of the already proposed variant of the composite photocatalyst [27], the structure of the granules of which is represented by three layers: adsorbent, silicon

dioxide, and photocatalyst - titanium dioxide anatase modification, will simultaneously solve problems: 1) effective adsorption of both polar and nonpolar (for example, pollutants); 2) exclusion of the influence of the electrically conductive properties of the sorbent on the recombination of photogenerated electron-hole pairs; 3) to ensure complete absorption of incident light by the particles of the photocatalyst, not the adsorbent; 4) detection of photocatalytic activity under visible light.

Today, thanks to the technological methods of reactions of "soft chemistry", it is possible to create substances with various structural features, to obtain metastable compounds by a sequence of low-temperature topochemical syntheses. Such reactions with a change in the structure and morphology of the particles take place at low temperatures while maintaining the basic structural features in perovskite-like layered oxide compounds. Depending on the nature and stoichiometry of their cations, they can exhibit a variety of physical and chemical properties: superconductivity, colossal magnetoresistance, ferroelectricity, catalytic and photocatalytic activity, the ability to ion exchange in solutions and melts, and the ability to hydrate. Therefore, the study of the peculiarities of transformations of intermediate precursors - alkaline coordination nitrates of REE, their reactivity during the synthesis of layered perovskite-like oxide phases directly affects the possible areas of further application of the latter.

For perovskite-like compounds, such researchers include, in particular, ion exchange [25], intercalation and deintercalation [28], various substitution and condensation processes [29], fission processes [30], and mutual transformations of one structure into another [31] (for example, the transition from Ruddlesden-Popper phases to Dion-Jacobson phases; transition within one type of phase with increasing or decreasing number of layers).

The most common reactions of "soft" chemistry are ion exchange reactions, during which the weakly bound cations of the interlayer space are replaced, while the perovskite layers are quite stable mainly due to metal-oxygen covalent bonds and play the role of a framework in the layered structure. This allows the substitution reactions of some interlayer cations to others, without affecting the basic structure of the layered oxide. Such reactions can be used to obtain a wide range of new perovskite-like structures.

For effective management of the properties of the received products, a deep understanding of physical and chemical processes, and the phenomena occurring during their formation are necessary. And their complex research with the application of modern physical and chemical methods allows improving our knowledge of characteristic features of fast-moving processes, stages of evolution of structure, and microstructure of technological objects.

The purpose and tasks of the study

To study the cooperative processes of interaction between structural components in the systems of nitrate precursors of REE representatives of the cerium subgroup and elements of IA subgroup of the periodic table

(Li, Na, K) in conditions similar to the regulations for creating multifunctional oxide materials for various purposes using photocatalytically active TiO₂ to form reliable ideas and obtaining objective knowledge about the features of transformations and the total behavior of the constituent elements in the preparatory stages of processing of technological objects with thermal activation (25-1000 °C), necessary for improving and developing methodologies and regulations of modern manufacturing technologies.

Experiment Methodology

To evaluate the possibility of controlling the processes of multistage formation of complex oxide compositions with multifunctional properties and substantiation of phase formation mechanisms as a model using a set of physicochemical methods, water-salt nitrate systems MeNO₃ - Ln(NO₃)₃ - H₂O, (Me - Li, Na, K; Ln - La-Sm) at 25-100 °C. The choice of the composition of the objects of study, temperature sections are determined by a number of factors.

First, among the elements of the rare earth series, the highest complexing ability is found by representatives of the cerium subgroup; among them, the largest changes in the composition, structure, and properties of their compounds are the elements of its middle, Pr and Nd. The selected components of the systems specify the technical characteristics of the target product or are modifiers of its properties. And the presence of a large number for the use of potential electronic analogues (representatives of natural series of rare earth, alkaline elements) causes significant variability and breadth of the range of modification of their characteristics. Temperature cross sections are due to the areas of the existence of crystal hydrate forms of the source components.

Secondly, according to [32], three layered potassium titanates K₂Ln₂Ti₃O₁₀ (Ln - La, Nd) of the above components, obtained by ceramic technology, in suspension form in aqueous-alcoholic solutions under the action of UV radiation show the highest among known species phases photocatalytic activity for the decomposition of H₂O and the release of hydrogen. This fact is associated with the morphology of their particles and the ability to reversibly intercalate water molecules in the interlayer space, which can lead to both an increase in the effective specific surface area of the photocatalyst and contribute to the spatial distribution of redox centers.

To determine the nature of chemical interaction and phase equilibria in water-salt systems of the studied nitrates (precursors of multicomponent oxide polyfunctional materials) in full concentration ratios in the temperature range of solutions using the method of additives described in [33, 34] and based on the study of solutions one of the properties of the most "sensitive" to the detection of phase transformations in systems, which is both a parameter of their state, and also simple experimental methods currently available. The method allows to find the limits of self-development to which the isolated system of the set structure goes in concrete conditions in an equilibrium state.

The equilibrium of the phases was reached within 2-3 days. Hydrated and anhydrous nitrates of these "c.f.a". elements were used as starting salts.

Chemical analysis of liquid and solid phases, "residues" was performed on the content of Ln³⁺ and nitrogen. The Ln³⁺ content was determined trilonometrically in the presence of xylenol orange as an indicator (acetate buffer solution, pH = 5-6) [35]; nitrogen - by distillation; Me⁺ ions - calculated by the difference, based on the total nitrate content and partly on the dry residue.

The obtained data for individual ions were converted into salt content and plotted on the solubility diagrams according to the principle of conformity. Graphical representation of the composition of solid phases formed in the system was performed according to Screenmakers [33, 34], confirmation of their individuality and characterization - chemical, crystal-optical, X-ray phase, X-ray structural, IR spectroscopic, thermographic, and other methods.

Crystal-optical determinations of the compounds were performed by the immersion method using a MIN-8 microscope. Phase analysis was performed on a DRON-3M diffractometer (Cu K α radiation, Ni filter) by the "powder" method. Diffractograms were deciphered from the PDF file JCPDS. Determination of symmetry, parameters of unit cells, and measurement of the intensity of diffraction reflections from single crystals was performed on an automatic X-ray single crystal diffractometer CAD - 4F "Enraf - Nonius" (Mo K α - radiation, graphite monochromator; ω / 2θ - method). All calculations for the determination and refinement of atomic structures were performed using complexes of crystallographic programs SHELX, XTL - SM, AREN. The IR absorption spectra of the synthesized compounds in the region of 400-4000 cm⁻¹ were recorded on a UR - 20 spectrophotometer using a standard vaseline oil suspension technique. Thermogravimetric analysis was performed on a Q - 1500 D derivatograph at temperatures from 293 K to 1273 K in the air with a heating rate of 10 degrees. / min and the developed device for DTA.

Basic material and results

Generalized and important for practical use information on alkaline coordination nitrates of rare earth elements of the cerium subgroup - precursors of promising modern multifunctional materials - on the conditions of their formation and existence, nature of the chemical bond, composition, structure, type of ligand coordination, the existence of isotope series on stoichiometry, composition the structures of the revealed properties are systematized by authors and in the most obvious form have resulted in tab. 1-4. The choice of this form of data presentation is the most informative and useful in the development of innovative projects that allows predicting the causal fundamental patterns of behavior of structural components in similar production processes, to choose the right modes, stages, methods of forming, and obtaining target products with reproducible structurally sensitive characteristics.

Table 1 – Isothermal concentration limits of crystallization of alkaline coordination nitrates of neodymium from solutions of water-salt systems $\text{MeNO}_3 - \text{Nd}(\text{NO}_3)_3 - \text{H}_2\text{O}$ (Me – Li, Na, K)

The composition of the compounds	t, °C	Compositions of saturated solutions corresponding to transition and eutonic points, wt. %		The nature of solubility
		MeNO_3	$\text{Nd}(\text{NO}_3)_3$	
$\text{Li}_3[\text{Nd}_2(\text{NO}_3)_9] \cdot 3\text{H}_2\text{O}$	65	19,32 13,95	59,61 65,63	incongruent
	100	24,03 9,68	54,68 72,51	congruent
$\text{Na}_2[\text{Nd}(\text{NO}_3)_5] \cdot \text{H}_2\text{O}$	50	16,55 8,60	51,62 62,58	incongruent
	65	20,44 3,03	50,40 70,17	incongruent
	100	25,27 4,15	47,28 76,96	incongruent
$\text{K}_2[\text{Nd}(\text{NO}_3)_5 (\text{H}_2\text{O})_2]$	50	27,26 21,34	51,62 54,91	incongruent
$\text{K}_3[\text{Nd}_2(\text{NO}_3)_9] \cdot \text{H}_2\text{O}$	50	21,34 11,49	54,91 63,31	incongruent
	65	32,57 8,67	47,88 70,44	congruent
	100	40,15 3,39	45,02 76,44	congruent

The revealed regularities in the nature of the behavior of structural components in rubidium, cesium nitrate systems La - Sm, in objects based on REE of the yttrium subgroup (Y, Gd - Lu) indicate the possibility of only limited or special application of the latter predecessors in the study area. There are a number of objective and economic reasons for this. These are the features of the electronic structure of their atoms, lower manifestation of chemical activity and complex-forming ability of these Ln^{3+} in comparison with the elements of the cerium subgroup, weaker effect of the considered influencing factors on the studied processes. To clarify the general patterns and build a holistic objective picture of the behavior of such technological precursors, the authors studied the systems of natural series Y, La - Lu, Li - Cs. Analysis of the results of the study was published in previous works of the authors [10, 11, 36].

In ternary REE-containing nitrate precursor systems, which are integral components of more complex multi-component systems, exchange transformations begin from the moment the components are dissolved in water. It was found that the Ln^{3+} cerium subgroup in the studied conditions is active complexing agents, that form anionic coordination compounds of Me^+ of all alkali metals, and their stability and complex of inherent properties are potent technological factors that significantly affect the nature of transformations in systems as intermediates. and the results of processes in general.

The obtained information allows modeling the behavior of structural components at the preparatory stages of the formation of modern multifunctional photocatalytically active materials according to innovative technological regulations with the use of nitrate REE-containing precursors.

The available identified trends in phase formation in the model systems studied are thermodynamically the most probable limits of transformations in technological objects in the conditions of formation and production of target products. And possible real deviations in such systems are caused by inhomogeneity of the reaction medium in composition, the content of reacting components, conditions of their location, finiteness of transformations, diffusion features, heat capacity, viscosity, nature of transformations at the boundaries of formed hetero phases, using their applied principles and methods. activation and other specific factors. And the identified processes of complexation in aqueous solutions of nitrates contribute to the homogenization of systems of structural components at the molecular level in complex or combined processing.

The analysis of the obtained data indicates the flow of competing processes of replacement of water molecules by nitrate ions in the systems in the immediate vicinity of the Ln^{3+} complexing agent. The degree of completeness of substitution depends on the nature of Ln^{3+} , the presence of Me^+ , the properties of electron-donor oxygen atoms and the spatial structure of ligands, the concentration of anions, the amount of solvent. A significant influence of the temperature factor on these processes is revealed. There are differences in the complexing ability of the elements of cerium and yttrium subgroups, Y, as well as among REE in the middle of the first subgroup. The obtained results indicate the gradual processes of complexation. The presence of certain values of the temperature at the beginning of the release into the solid phase of complex compounds - the existence of an energy barrier and the need for some activation energy to carry out such transformations. In the formation of nitrate complexes, the requirements

of symmetry are largely met, and the planar small-sized ligand NO_3^- is “convenient” for the formation of a highly symmetric environment of the Ln_3^+ ion. Lanthanides have a tendency to form three types of NO_3^- ligand coordination. This leads to the formation of both isolated complexes and their polymerization into dual-core, chains, and frameworks.

All established coordination compounds were synthesized in single crystal form and characterized by a set of physicochemical methods. Table 2 shows the X-ray diffraction characteristics of the newly formed phases for the possibility of their identification and detection during processing.

Table 2 – Radiographic data of neodymium lithium, sodium, potassium coordination nitrates

$\text{Li}_3[\text{Nd}_2(\text{NO}_3)_9] \cdot 3\text{H}_2\text{O}$				$\text{Na}_2[\text{Nd}(\text{NO}_3)_5] \cdot \text{H}_2\text{O}$		$\text{K}_2[\text{Nd}(\text{NO}_3)_5 (\text{H}_2\text{O})_2]$				$\text{K}_3[\text{Nd}_2(\text{NO}_3)_9] \cdot \text{H}_2\text{O}$			
d, Å	I/I ₀ , %	d, Å	I/I ₀ , %	d, Å	I/I ₀ , %	d, Å	I/I ₀ , %	d, Å	I/I ₀ , %	d, Å	I/I ₀ , %	d, Å	I/I ₀ , %
8,36	30	2,013	19	7,84	63	5,42	66	2,056	24	9,48	85	2,281	21
7,64	77	1,979	19	7,54	47	5,27	90	1,993	27	7,74	92	2,249	69
6,68	13	1,944	28	7,07	73	4,94	45	1,947	26	7,65	32	2,189	54
6,00	38	1,931	26	5,18	27	4,11	72	1,777	11	5,36	39	2,108	68
5,75	79	1,855	15	4,23	100	3,88	15	–	–	5,27	40	2,082	37
5,42	98	1,778	15	3,80	57	3,80	42	–	–	4,94	30	2,058	15
5,26	74	1,726	28	3,15	23	3,66	12	–	–	4,76	46	2,012	49
4,76	51	1,708	34	3,09	67	3,53	42	–	–	4,49	87	1,909	21
4,64	100	–	–	3,02	86	3,35	38	–	–	4,26	27	1,837	27
4,35	43	–	–	2,629	20	3,18	13	–	–	4,06	100	1,757	19
4,19	47	–	–	2,391	17	3,05	73	–	–	3,89	40	1,729	16
3,94	51	–	–	2,346	17	2,873	17	–	–	3,78	22	1,714	18
3,90	40	–	–	2,307	8	2,843	33	–	–	3,73	39	–	–
3,56	26	–	–	2,234	13	2,783	14	–	–	3,36	19	–	–
3,32	19	–	–	2,178	27	2,750	17	–	–	3,27	26	–	–
3,22	47	–	–	1,979	13	2,724	40	–	–	3,18	55	–	–
2,978	34	–	–	–	–	2,664	14	–	–	3,07	16	–	–
2,772	19	–	–	–	–	2,639	19	–	–	3,04	17	–	–
2,617	28	–	–	–	–	2,594	100	–	–	2,844	20	–	–
2,545	43	–	–	–	–	2,463	37	–	–	2,755	12	–	–
2,385	21	–	–	–	–	2,392	19	–	–	2,730	18	–	–
2,328	17	–	–	–	–	2,374	44	–	–	2,647	55	–	–
2,305	23	–	–	–	–	2,314	15	–	–	2,592	16	–	–
2,226	19	–	–	–	–	2,235	25	–	–	2,508	87	–	–
2,135	49	–	–	–	–	2,188	10	–	–	2,468	78	–	–
2,111	43	–	–	–	–	2,099	21	–	–	2,349	32	–	–

Note: d, Å - interplanar distances; I/I₀, % - the relative intensities of the reflexes.

The authors conducted a crystal chemical analysis of alkaline rare earth nitrate compounds, which is based on the results of our own research [37, 11] and literature data [38]. Particular attention is paid to the structure of coordination polyhedra Ln, which largely determines the basic properties of the corresponding compounds. Analyzing the shape, symmetry, and other properties of polyhedra (see Table 3), we get the opportunity to approach the understanding of the individual features of REE.

Data on average Ln - O distances in rare earth nitrates of alkaline cations discussed in this paper are in good agreement with the expected tendency to decrease Ln - O distances according to lanthanide compression and to increase these distances with increasing coordination number for fixed REE ion. The distances Ln - O (H_2O), as a rule, are among the shortest contacts in polyhedra. This fact can be explained on the basis of the presence of competing interactions with bonds of the type Ln - O (NO_3^-). Coordination polyhedra are composed, as a

rule, of oxygen atoms of bidentate coordinated nitrate groups, less often in combination with oxygen atoms of water molecules. In all considered compounds coordination numbers of representatives of lanthanides of cerium subgroup 12.

When summarizing the structural data of alkaline coordination nitrates, REE draws attention to the extremely limited range of coordination polyhedra for such high CN REEs. In Fig. 2 shows a general view of the identified types of icosahedrons found in the structures of the studied compounds. In cases where water is not part of the coordination sphere of the Ln atom, the polyhedra are constructed in exactly the same way (Fig. 2a). Their equivalence is that the shortened O - O ribs (common to NO_3^- - ligands) occupy the same positions. Exceptions are one of the 2 independent polyhedra Ln in two isostructural compounds $\text{Li}_3[\text{Ln}_2(\text{NO}_3)_9] \cdot 3\text{H}_2\text{O}$ (Ln - La, Nd) (Fig. 2b). If the coordination saturation occurs with the participation of water molecules, the shape of the 12-vertices changes

slightly. Topologically, it is still the same icosahedron. However, the distribution of shortened ribs in this case is different (Fig. 2c).

The analysis of the Ln-polyhedra considered by us gives grounds to note the tendency of REE in this class of compounds to the organization of a symmetric coordination environment. In some cases, despite the fact that Ln³⁺ ions are located in common positions, their coordination polyhedra have at least one noncrystallographic axis of symmetry 2 (see Table 3).

The following data from the thermographic study of lithium, sodium, potassium coordination nitrates of rare earth elements of the cerium subgroup (Fig. 3, Table 4) clarify the nature and patterns of thermal transformations of these compounds in the temperature range 25-1000 °C, establish their heat resistance, intervals, staged processes, phase formation depending on the composition, content, nature of the components, the method of packing coordination polyhedra in spatial

construction, conditions and method of processing, etc. This makes it possible to predict the behavior of the applied potential predecessors in real technological systems in similar conditions. For comparison and analysis there is information about the low stability and heat resistance of potassium coordination nitrates Y, Gd - Lu composition K[Ln(NO₃)₄(H₂O)₂], which leads to limitations in the use of this type of precursors in technological transformations to modify the properties target products.

It was found that the coordination numbers of the Ln³⁺ cerium subgroup - 12, found in low-temperature associated forms, remain unchanged until the formation of stable high-temperature multicomponent oxide phases MeLnO₂, Me₂Ln₂Ti₃O₁₀. This indicates the feasibility of using alkaline coordination nitrate REE-containing precursors in such technological innovative solutions.

Table 3 – Coordination polyhedra of Ln atoms in alkaline rare earth nitrates

Compound	D ₁	D ₂	D ₃	C. N	Polyhedron type, its symmetry
Li ₃ [La ₂ (NO ₃) ₉]·3H ₂ O		2,66	2,66	12	Ic 4L ₃ 3L ₂
		2,65	2,65	12	Ic L ₃ 3L ₂
Li ₃ [Nd ₂ (NO ₃) ₉]·3H ₂ O		2,61	2,61	12	Ic 4L ₃ 3L ₂
		2,60	2,60	12	Ic L ₃ 3L ₂
Na ₂ [Nd(NO ₃) ₅]·H ₂ O		2,62	2,62	12	Ic L ₃ 3L ₂
		2,61	2,61	12	Ic L ₃ 3L ₂
		2,61	2,61	12	Ic L ₃ 3L ₂
K ₂ [La(NO ₃) ₅ (H ₂ O) ₂]	2,70	2,68	2,68	12	Ic L ₂
K ₂ [Nd(NO ₃) ₅ (H ₂ O) ₂]	2,62	2,61	2,61	12	Ic L ₂
K ₃ [Pr ₂ (NO ₃) ₉]		2,63	2,63	12	Ic L ₃ 3L ₂
K ₃ [Nd ₂ (NO ₃) ₉]		2,61	2,61	12	Ic L ₃ 3L ₂
(NH ₄) ₂ [La(NO ₃) ₅ (H ₂ O) ₂]·H ₂ O	2,54	2,70	2,67	12	Ic L ₃ 5L ₂
(NH ₄) ₂ [La(NO ₃) ₅ (H ₂ O) ₂]·2H ₂ O	2,59	2,70	2,68	12	Ic L ₃ 5L ₂
(NH ₄) ₂ [Pr(NO ₃) ₅ (H ₂ O) ₂]·2H ₂ O	2,54	2,66	2,64	12	Ic L ₃ 5L ₂

D₁, D₂, D₃ – average distance (Å) <Ln–O_{H2O}>, <Ln–O_{NO3}>, <Ln–O>; Ic – icosahedron

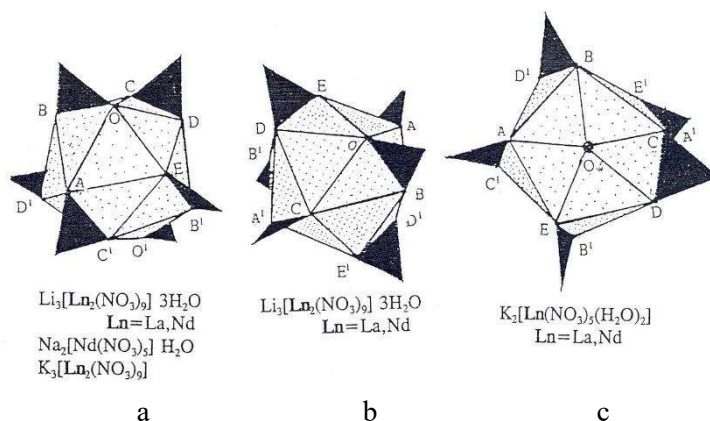


Figure 2 – Schematic representation and general view of Ln-icosahedrons found in the structures of the REEs of the cerium subgroup and lithium, sodium, and potassium

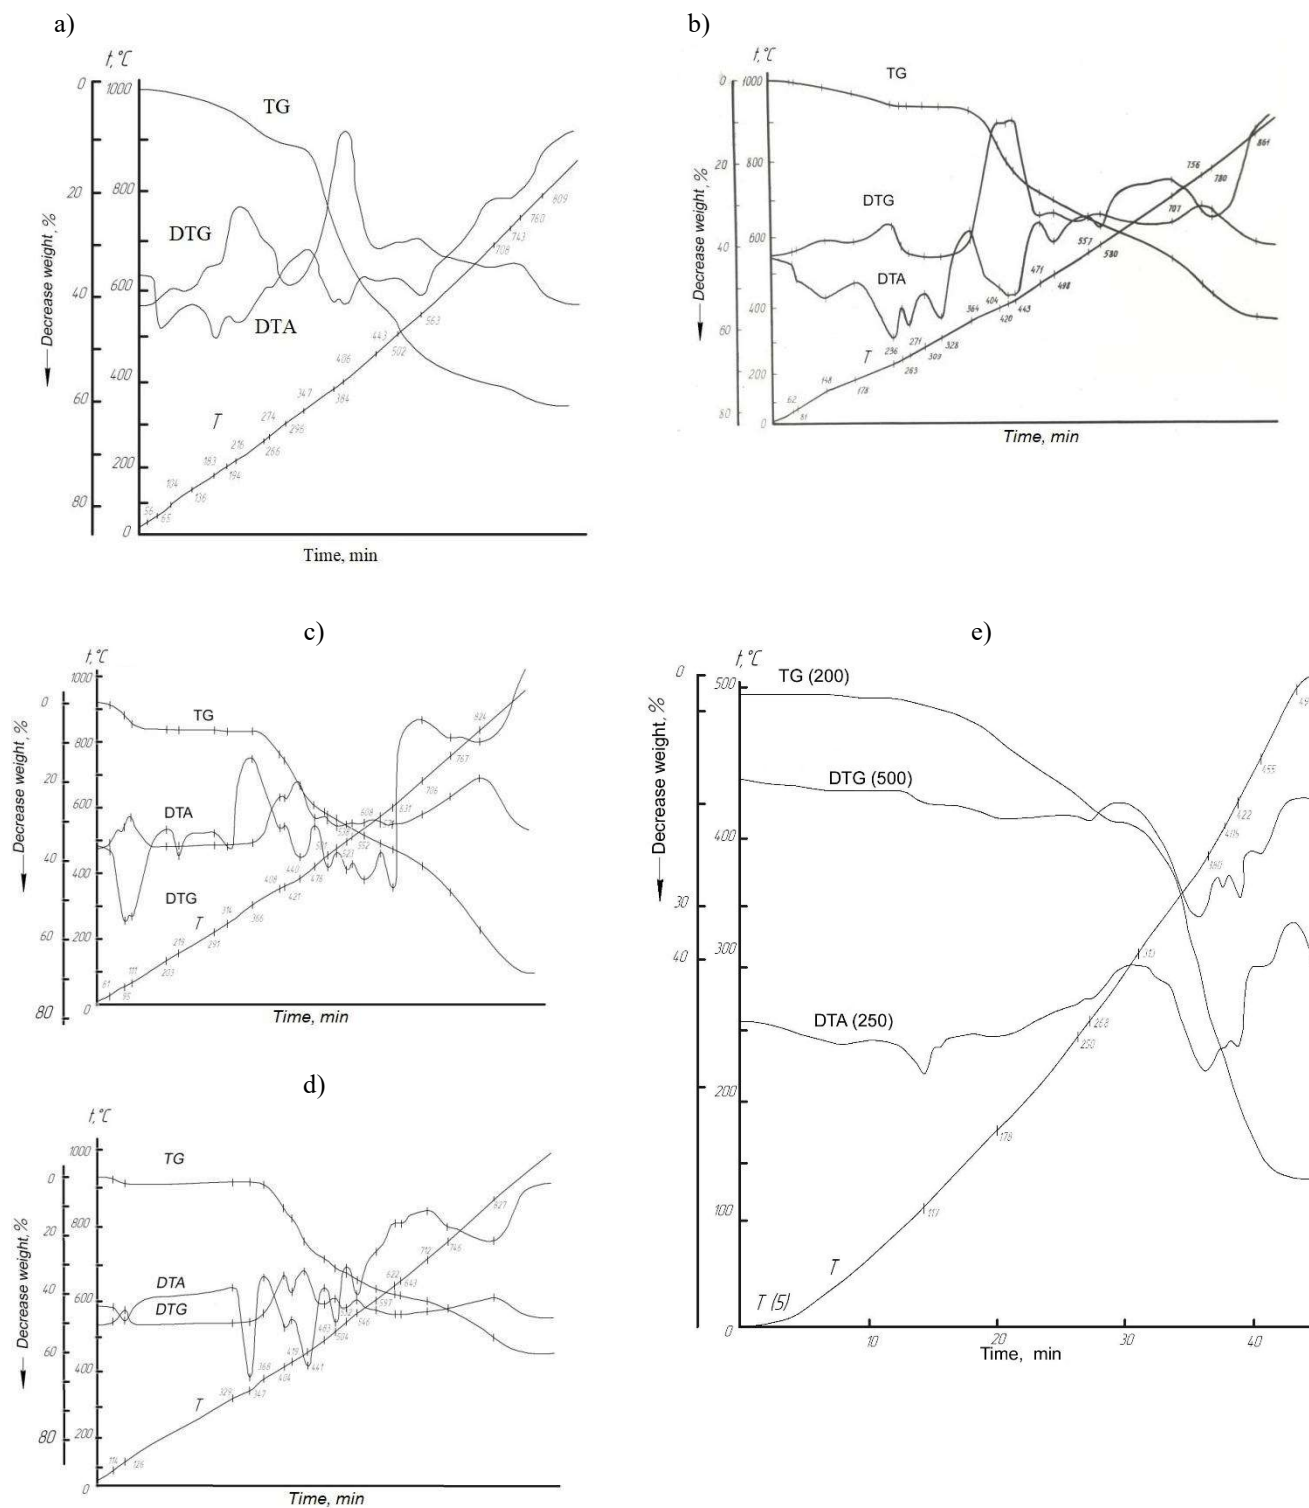


Figure 3 – Derivative diagrams:
a – $\text{Li}_3[\text{Nd}_2(\text{NO}_3)_9] \cdot 3\text{H}_2\text{O}$; b – $\text{Na}_2[\text{Nd}(\text{NO}_3)_5] \cdot \text{H}_2\text{O}$;
c – $\text{K}_2[\text{Nd}(\text{NO}_3)_5(\text{H}_2\text{O})_2]$; d – $\text{K}_3[\text{Nd}_2(\text{NO}_3)_9] \cdot \text{H}_2\text{O}$;
e – $\text{K}[\text{Yb}(\text{NO}_3)_4(\text{H}_2\text{O})_2]$ (Ln – Y, Gd–Lu)
 T – temperature curve; DTA – differential temperature curve;
 TG – thermogravimetric curve; DTG – differential thermogravimetric curve

Table 4 – The temperature values of the detected effects during the heat treatment of the representatives of the established groups of alkali coordination nitrates REE

Compounds; spatial group of crystals	Representatives	Temperature interval of formation, °C	The nature of solubility	Dehydration	Melting in crystallization water	Polymorphic transitions	Melting anhydrous form	The composition of the products of conversion at 980°C
$\text{Li}_3[\text{Ln}_2(\text{NO}_3)_9] \cdot 3\text{H}_2\text{O}$ cubic.; $P2_13$	La – Sm	65-100	congr.	65 183 216	183	–	274	LiLnO_2
$\text{Na}_2[\text{Ln}(\text{NO}_3)_5] \cdot \text{H}_2\text{O}$ monocl.; $P2_1/a$	La – Sm	50-100	congr.	81 148 236	–	271	328	NaLnO_2
$\text{K}_2[\text{Ln}(\text{NO}_3)_5(\text{H}_2\text{O})_2]$ rhomb.; $Fdd2$	La – Nd	50-100	incongr.	95,111	95	219	314	$\text{KLnO}_2, \text{Ln}_2\text{O}_3$
$\text{K}_3[\text{Ln}_2(\text{NO}_3)_9] \cdot \text{H}_2\text{O}$ cubic.; $P4_332$	La – Sm	50	congr.	126	–	–	347	Ln_2O_3
$\text{K}[\text{Ln}(\text{NO}_3)_4(\text{H}_2\text{O})_2]$ prim. rhomb.; $P2_1cn$	Y, Gd - Lu	50-100	congr.	138, 172	138	–	–	Ln_2O_3

Scientific novelty

A comprehensive systematic study of the interaction of structural components in systems of rare earth nitrates and IA groups of elements of the periodic table - precursors of modern multicomponent oxide functional materials based on them - established the formation of a wide class of alkaline coordination nitrates of lanthanides. The identified objective patterns have a fundamental and applied value, and deepen the understanding of:

- the chemical and physical properties of Ln, their complexing ability,
- the possibility of formation and existence in similar systems of associated new phases, their atomic-crystal-line structure, stability, and stability,
- the influence of the nature of lanthanides and alkali metals on the structure of complex anions and compounds in general,
- the individuality of Ln complexes,
- the existence of isotopic in composition and structure of groups of compounds in the natural series of lanthanides and alkali metals,
- the role of NO_3^- - groups in the stereochemistry of this class of nitrates,
- the role of water in the formation of the immediate environment of Ln^{3+} ions-complexing agents.

Practical significance

The obtained system of knowledge about transformation processes in REE-containing nitrate precursor systems and crystal chemical properties of Ln coordination nitrate samples acquires special value in the formation of nanostructured layered perovskite-like compounds of lanthanides and transition elements (including titanium, described in [7, 12, 32, 39, 40], others), solid solutions based on them; in establishing technological and functional dependencies between the method of preparation, variability of the method of activation of technological systems, methodology of manufacturing the target product and its phase composition, lattice parameters, specific surface area, the morphology of constituent particles, the activity of self-cleaning compositions with photocatalytic and hydrophilic properties. and special structural elements; in the practical implementation of innovative projects of water decomposition for the purposes of hydrogen production (as an alternative fuel), decomposition of toxic organic substances in solutions and air, incomplete oxidation of carbohydrates; in obtaining other perovskite-like phases by ion exchange reactions and in other areas.

Conclusions

1. The results of the study show that the processes of obtaining oxide REE-containing structural and functional materials for different purposes using nitrates of elements of different electronic structures by chemical mixing of the source components in the joint separation of products from the liquid phase by sequential or co-precipitation followed by heat treatment. Data on their composition, content, and behavior in each case require prior systemic empirical knowledge in full concentration ratios in a given temperature range.

2. Differences in the behavior of structural components in the systems of lanthanides of cerium and yttrium subgroups, in their nature of the interaction, stages, features, and patterns of flow.

3. The new knowledge is the basis for:

- finding ways to increase the activity of Ln-forms;
- elucidation of the nature of successive thermal transformations in nitrate REE-containing multicomponent systems of different aggregate states during their heat treatment; conditions of formation and existence, properties of intermediate phases; influencing factors; possible ways to control the receipt of the target product;
- in case of creation of modern perfect low-cost technologies of formation of functional materials of various functions with reproducible properties.

References

1. Мазуренко Е.А., Герасемчук А.И., Трунова Е.К. и др. (2004). Координационные соединения металлов – прекурсоры функциональных материалов. *Український хімічний журнал*, 70, 32-37
2. Белоус А.Г. (2009). Некоторые тенденции развития функциональных материалов на основе сложных оксидных систем. *Український хімічний журнал*, 75, 3-14
3. Zhang Q., Schmidt N., Lan J. et al. (2014). A facile method for the synthesis of the $\text{Li}_{0.3}\text{La}_{0.57}\text{TiO}_3$ solid state electrolyte. *Chemical Communications*, 50, 5593-5596
4. Гавриленко О.М., Пашкова О.В., Білоус А.Г. (2005). Кристалохімічні особливості та властивості Li^+ , $\{\text{Na}^+, \text{K}^+\}$ -заміщених ніобатів лантану і структурною дефектного перовскіту. *Український хім. журнал*, 71, 73-77
5. Moure C. and Peña O. (2015). Recent advances in perovskites: Processing and properties. *Progress in Solid State Chemistry*, 43, 123-148
6. Белоус А.Г. (2008). Сложные оксиды металлов для сверхвысокочастотных и высокопроницаемых диэлектриков. *Український хімічний журнал*, 74, 3-21
7. Shi J. and Guo L. (2012). ABO_3 -based photocatalysts for water splitting. *Progress in Natural Science: Materials International*, 22(6), 592-615
8. Schaak R.E., Mallouk T.E. (2012). Perovskites by Design: A Toolbox of Solid-State Reactions. *Chemistry of Materials*, 14(4), 1455-1471
9. Verma A.S., Jinda V.K. (2010). ABX_3 -type oxides and halides: their structure and physical properties in Perovskites: Structure, Properties and Uses. *Nova Science Publishers, Inc.*, 176, 463-479
10. Дрючко О.Г., Стороженко Д.О., Бунякіна Н.В., Коробко Б.О. (2018). Фізико-хімічне охарактеризування координаційних нітратів РЗЕ і лужних металів – прекурсорів оксидних поліфункціональних матеріалів. *Вісник НТУ «ХПІ». Хімія, хімічна технологія та екологія*, 39(1315), 3-13
<https://doi:10.20998/2079-0821.2018.39.01>
11. Dryuchko O., Storozhenko D., Vigdorichik A., Bunyakina N., Ivanytska I., Kytaihora K., Khaniukov V. (2019). Features of transformations in REE-containing systems of nitrate precursors in preparatory processes of formation of multifunctional oxide materials. *Molecular Crystals and Liquid Crystals*, 72(1), 199-214
<https://doi.org/10.1080/15421406.2018.1542066>
12. Xianhong Zhang, Anji Zhang, Haiyin Zhang, Jihe Luo, Lily Chen (2011). Pat. CN. 102382490A. *Preparation and application of a hydrophilic self-cleaning coating with photocatalytic activity*. Claimed
1. Mazurenko E.A., Gerasemchuk A.I., Trunova E.K. et al. (2004). Coordination compounds of metals – precursors of functional materials. *Ukrainian Chemistry Journal*, 70, 32-37
2. Belous A.G. (2009). Some trends in the development of functional materials based on complex oxide systems. *Ukrainian Chemistry Journal*, 75, 3-14
3. Zhang Q., Schmidt N., Lan J. et al. (2014). A facile method for the synthesis of the $\text{Li}_{0.3}\text{La}_{0.57}\text{TiO}_3$ solid state electrolyte. *Chemical Communications*, 50, 5593-5596
4. Gavrilenko O.M., Pashkova O.V., Bilous A.G. (2005). Crystallochemical properties and properties of Li^+ , $\{\text{Na}^+, \text{K}^+\}$ -substituted niobates of lanthanum and the structure of defective perovskite. *Ukrainian Chemistry Journal*, 71, 73-77
5. Moure C. and Peña O. (2015). Recent advances in perovskites: Processing and properties. *Progress in Solid State Chemistry*, 43, 123-148
6. Belous A.G. (2008). Complex metal oxides for super-high-frequency and high-permeability dielectrics. *Ukrainian Chemistry Journal*, 74, 3-21
7. Shi J. and Guo L. (2012). ABO_3 -based photocatalysts for water splitting. *Progress in Natural Science: Materials International*, 22(6), 592-615
8. Schaak R.E., Mallouk T.E. (2012). Perovskites by Design: A Toolbox of Solid-State Reactions. *Chemistry of Materials*, 14(4), 1455-1471
9. Verma A.S., Jinda V.K. (2010). ABX_3 -type oxides and halides: their structure and physical properties,” in Perovskites: Structure, Properties and Uses. *Nova Science Publishers, Inc.*, 176, 463-479
10. Drjuchko O.G., Storozhenko D.O., Bunjakina N.V., Korobko B.O. (2018). Physico-chemical characterization of coordination nitrates of REE and alkali metals – precursors of oxide polyfunctional materials. *Bulletin of the NTU «KhPI». Chemistry, Chemical Technology and Ecology*, 39(1315), 3-13
<https://doi:10.20998/2079-0821.2018.39.01>
11. Dryuchko O., Storozhenko D., Vigdorichik A., Bunyakina N., Ivanytska I., Kytaihora K., Khaniukov V. (2019). Features of transformations in REE-containing systems of nitrate precursors in preparatory processes of formation of multifunctional oxide materials. *Molecular Crystals and Liquid Crystals*, 72(1), 199-214
<https://doi.org/10.1080/15421406.2018.1542066>
12. Xianhong Zhang, Anji Zhang, Haiyin Zhang, Jihe Luo, Lily Chen (2011). Pat. CN. 102382490A. *Preparation and application of a hydrophilic self-cleaning coating with photocatalytic activity*. Claimed

13. Varma A., Mukasyan A.S., Rogachev A.S. et al. (2016). Solution Combustion Synthesis of Nanoscale Materials. *American Chemical Society. Chemical Reviews*, 116, 14493-14586
14. Seeber A., Klein A.N., Speller C.V. et al. (2010). Sintering Unalloyed Titanium in DC Electrical Abnormal Glow Discharge. *Materials Research*, 13(1), 99-106
15. Fujishima A., Zhang X., Tryck D.A. (2008). TiO₂ photocatalysis and related surface phenomena. *Surface Science Reports*, 63(12), 515-582
16. Zhang L., Ji M., Wang H., Lu L., Yang X., Wang X. (2006). Stearic acid sol-gel synthesis of ultrafinelayered K₂Nd₂Ti₃O₁₀ at low temperature and its acid-exchanging property. *Mater. Lett.*, 60(25-26), 3100-3103
17. Lagaly G. (1986). Interaction of alkylamines with different types of layered compounds. *Solid State Ionics*, 1(22), 43-51
18. Machida M., Miyazaki K., Matsushima S. et al. (2003). Photocatalytic properties of layered perovskite tantalates, MLnTa₂O₇ (M = Cs, Rb, Na, and H; Ln = La, Pr, Nd, and Sm). *J. Mater. Chem*, 6(13), 1433-1445
19. Silyukov O., Chislov V., Burovikhina A. et al. (2012). Thermogravimetry study of ion exchange and hydration in layered oxide materials *J. Therm. Anal. Calorim*, 1(110), 187-192
20. Gopalakrishnan J., Sivakumar T., Ramesha K. et al. (2000). Transformations of Ruddlesden-Popper oxides to new layered perovskite oxides by metathesis reactions. *Chem. Phys*, 9, 6237-6241
21. Schaak R.E., Mallouk T.E. (2001). KLnTiO₄ (Ln=La, Nd, Sm, Eu, Gd, Dy): A New Series of Ruddlesden-Popper Phases Synthesized by Ion-Exchange of HLnTiO₄. *J. Solid State Chem*, 161(2), 225-232
22. Zhu W.J., Feng H.H., Hor P.H. (1996). Synthesis and characterization of layered titanium oxides NaRTiO₄ (R = La, Nd and Gd). *Materials Research Bulletin*, 31(1), 107-111
23. Toda M., Watanabe K., Sato J. (1996). Crystal structure determination of ion-exchangeable layered perovskite compounds, K₂La₂Ti₃O₁₀ and Li₂La₂Ti₃O₁₀. *Materials Research Bulletin*, 31(11), 1427-1435
24. Richard M., Brohan L., Tournoux M. (1993). Synthesis, characterization, and acid exchange of the layered perovskites A₂Nd₂Ti₃O₁₀ (A = Na, K). *J. Solid State Chem.*, 112, 345-354
25. Gopalakrishnan J., Bhat V. (1987). A₂Ln₂Ti₃O₁₀ (A = potassium or rubidium; Ln = lanthanum or rare earth): a new series of layered perovskites exhibiting ion exchange. *Inorganic Chemistry*, 26, 4299-4301
26. Utkina T., Chislov M., Silyukov O., Burovikhina A., Zvereva I. (2016). TG and DSC investigation of water intercalation and protonation processes in perovskite-like layered structure of titanate K₂Nd₂Ti₃O₁₀. *Journal of Thermal Analysis and Calorimetry*, 125, 281-287
27. Takanabe K. (2017). Photocatalytic Water Splitting: Quantitative Approaches toward Photocatalyst by Design. *ACS Catal.* 7, 8006-8022
28. Kato M., Kajita T., Hanakago R. et al. (2006). Search for new superconductors by the Liintercalation into layered perovskites. *Phys. C Supercond*, 445, 26-30
29. Thangadurai V., Subbanna G.N. & Gopalakrishnan J. (1998). Ln₂Ti₂O₇ (Ln = La, Nd, Sm, Gd): a novel series of defective Ruddlesden-Popper phases formed by topotactic dehydration of HLnTiO₄. *Chemical Communications*, 7, 1299-1300
30. Ranmohotti K.G.S., Josepha E., Choi J. et al. (2011). Topochemical manipulation of perovskites: low-temperature reaction strategies for directing structure and properties. *Advanced Materials*, 23(4), 442-460
13. Varma A., Mukasyan A.S., Rogachev A.S. et al. (2016). Solution Combustion Synthesis of Nanoscale Materials. *American Chemical Society. Chemical Reviews*, 116, 14493-14586
14. Seeber A., Klein A.N., Speller C.V. et al. (2010). Sintering Unalloyed Titanium in DC Electrical Abnormal Glow Discharge. *Materials Research*, 13(1), 99-106
15. Fujishima A., Zhang X., Tryck D.A. (2008). TiO₂ photocatalysis and related surface phenomena. *Surface Science Reports*, 63(12), 515-582
16. Zhang L., Ji M., Wang H., Lu L., Yang X., Wang X. (2006). Stearic acid sol-gel synthesis of ultrafinelayered K₂Nd₂Ti₃O₁₀ at low temperature and its acid-exchanging property. *Mater. Lett.*, 60(25-26), 3100-3103
17. Lagaly G. (1986). Interaction of alkylamines with different types of layered compounds. *Solid State Ionics*, 1(22), 43-51
18. Machida M., Miyazaki K., Matsushima S. et al. (2003). Photocatalytic properties of layered perovskite tantalates, MLnTa₂O₇ (M = Cs, Rb, Na, and H; Ln = La, Pr, Nd, and Sm). *J. Mater. Chem*, 6(13), 1433-1445
19. Silyukov O., Chislov V., Burovikhina A. et al. (2012). Thermogravimetry study of ion exchange and hydration in layered oxide materials *J. Therm. Anal. Calorim*, 1(110), 187-192
20. Gopalakrishnan J., Sivakumar T., Ramesha K. et al. (2000). Transformations of Ruddlesden-Popper oxides to new layered perovskite oxides by metathesis reactions. *Chem. Phys*, 9, 6237-6241
21. Schaak R.E., Mallouk T.E. (2001). KLnTiO₄ (Ln=La, Nd, Sm, Eu, Gd, Dy): A New Series of Ruddlesden-Popper Phases Synthesized by Ion-Exchange of HLnTiO₄. *J. Solid State Chem*, 161(2), 225-232
22. Zhu W.J., Feng H.H., Hor P.H. (1996). Synthesis and characterization of layered titanium oxides NaRTiO₄ (R = La, Nd and Gd). *Materials Research Bulletin*, 31(1), 107-111
23. Toda M., Watanabe K., Sato J. (1996). Crystal structure determination of ion-exchangeable layered perovskite compounds, K₂La₂Ti₃O₁₀ and Li₂La₂Ti₃O₁₀. *Materials Research Bulletin*, 31(11), 1427-1435
24. Richard M., Brohan L., Tournoux M. (1993). Synthesis, characterization, and acid exchange of the layered perovskites A₂Nd₂Ti₃O₁₀ (A = Na, K). *J. Solid State Chem.*, 112, 345-354
25. Gopalakrishnan J., Bhat V. (1987). A₂Ln₂Ti₃O₁₀ (A = potassium or rubidium; Ln = lanthanum or rare earth): a new series of layered perovskites exhibiting ion exchange. *Inorganic Chemistry*, 26, 4299-4301
26. Utkina T., Chislov M., Silyukov O., Burovikhina A., Zvereva I. (2016). TG and DSC investigation of water intercalation and protonation processes in perovskite-like layered structure of titanate K₂Nd₂Ti₃O₁₀. *Journal of Thermal Analysis and Calorimetry*, 125, 281-287
27. Takanabe K. (2017). Photocatalytic Water Splitting: Quantitative Approaches toward Photocatalyst by Design. *ACS Catal.* 7, 8006-8022
28. Kato M., Kajita T., Hanakago R. et al. (2006). Search for new superconductors by the Liintercalation into layered perovskites. *Phys. C Supercond*, 445, 26-30
29. Thangadurai V., Subbanna G.N. & Gopalakrishnan J. (1998). Ln₂Ti₂O₇ (Ln = La, Nd, Sm, Gd): a novel series of defective Ruddlesden-Popper phases formed by topotactic dehydration of HLnTiO₄. *Chemical Communications*, 7, 1299-1300
30. Ranmohotti K.G.S., Josepha E., Choi J. et al. (2011). Topochemical manipulation of perovskites: low-temperature reaction strategies for directing structure and properties. *Advanced Materials*, 23(4), 442-460

31. Дрючко О.Г., Стороженко Д.О., Бунякіна Н.В., Коробко Б.О., Іваницька І.О., Пашченко А.М. (2016). Особливості перетворень в РЗЕ-вмісних системах нітратних прекурсорів у підготовчих процесах формування перовскітоподібних оксидних матеріалів. *Вісник національного технічного університету «ХПІ»: Хімія, хімічна технологія та екологія*, 22(1194), 63-71
32. Kawashima K., Hojamberdiev M., Wagata H., Yubuta K., Domen K., and Teshima K. (2017). Protonated Oxide, Nitrided, and Reoxidized $K_2La_2Ti_3O_{10}$ Crystals: Visible-Light-Induced Photocatalytic Water Oxidation and Fabrication of Their Nanosheets, *ACS Sustain. Chem.*, 5, 232-240
33. Топоров С.В. (2021). *Фізико-хімічні методи дослідження речовин та матеріалів*. Одеса: Одес. нац. ун-т ім. І. І. Мечникова.
34. Горощенко Я.Г. (1978). *Фізико-хімічний аналіз ізогенних і гетерогенних систем*. Київ: Наук. думка
35. Циганок Л.П. (2014). *Аналітична хімія. Хімічні методи аналізу*. Дніпро: ДНУ ім. О.Гончара
36. Storozhenko D.O., Dryuchko O.G., Bunyakina N.V., Ivanytska I.O. (2015). Phase Formation in REE-Containing Water-Salt Systems at the Preparatory Stages of the Multi-component Oxide Functional Materials Formation. *Innovations in Corrosion and Materials Science*, 5(2), 80-84
37. Vigdorichik A.G., Malinovskiy Yu.A., Dryuchko A.G. et al. (1992). Low-temperature X-ray structure analysis of potassium-neodymium nitrates $K_3[Nd_2(NO_3)_9]$ and $K_2[Nd(NO_3)_5(H_2O)_2]$. *Crystallography*, 37(4), 882-888
38. Eriksson B., Larrson L.O., Niinisto L. et al. (1980). Crystal and molecular structure of potassium diaquapentanitratolanthanate (III). *Acta Chemica Scandinavica*, 34(8), 567-572
39. Schaak R.E., Mallouk T.E. (2002). Perovskites by Design: A Toolbox of Solid-State Reactions. *Chemistry of Materials*, 14(4), 1455-1471
40. Mendoza E., Padmasree K.P., Montemayor S.M. et al. (2012). Molten salts synthesis and electrical properties of Sr- and/or Mg-doped perovskite-type $LaAlO_3$ powders. *Journal of Materials Science*, 47, 6076-6085
31. Dryuchko O.G., Storozhenko D.O., Bunyakina N.V., Korobko B.O., Ivanytska I.O., Pashchenko A.M. (2016). Peculiarities of transformations in REE-containing systems of nitrate precursors in preparatory processes of perovskite-like oxide materials formation. *Bulletin of the NTU «KhPI»: Chemistry, Chemical Technology and Ecology*, 22(1194), 63-71
32. Kawashima K., Hojamberdiev M., Wagata H., Yubuta K., Domen K., and Teshima K. (2017). Protonated Oxide, Nitrided, and Reoxidized $K_2La_2Ti_3O_{10}$ Crystals: Visible-Light-Induced Photocatalytic Water Oxidation and Fabrication of Their Nanosheets, *ACS Sustain. Chem.*, 5, 232-240
33. Toporov S.V. (2021). *Physico-chemical methods of research of substances and materials*. Odessa: Odessa. national University named after I. I. Mechnikova
34. Goroshchenko Ya.G. (1978). *Physical and Chemical Analysis of homogenous and heterogenous systems*. Kiev: Naukova dumka
35. Tsyganok L.P. (2014). *Analytical chemistry. Chemical methods of analysis*. Dnipro: DNU named after O. Honchar
36. Storozhenko D.O., Dryuchko O.G., Bunyakina N.V., Ivanytska I.O. (2015). Phase Formation in REE-Containing Water-Salt Systems at the Preparatory Stages of the Multi-component Oxide Functional Materials Formation. *Innovations in Corrosion and Materials Science*, 5(2), 80-84
37. Vigdorichik A.G., Malinovskiy Yu.A., Dryuchko A.G. et al. (1992). Low-temperature X-ray structure analysis of potassium-neodymium nitrates $K_3[Nd_2(NO_3)_9]$ and $K_2[Nd(NO_3)_5(H_2O)_2]$. *Crystallography*, 37(4), 882-888
38. Eriksson B., Larrson L.O., Niinisto L. et al. (1980). Crystal and molecular structure of potassium diaquapentanitratolanthanate (III). *Acta Chemica Scandinavica*, 34(8), 567-572
39. Schaak R.E., Mallouk T.E. (2002). Perovskites by Design: A Toolbox of Solid-State Reactions. *Chemistry of Materials*, 14(4), 1455-1471
40. Mendoza E., Padmasree K.P., Montemayor S.M. et al. (2012). Molten salts synthesis and electrical properties of Sr- and/or Mg-doped perovskite-type $LaAlO_3$ powders. *Journal of Materials Science*, 47, 6076-6085